

# Biodiesel Quality in Germany

Sampling results of biodiesel producers and  
Warehouse operators of  
Association Quality Management Biodiesel  
(AGQM)

**2023**



**Project Management and Report:**

Katharina Friedrich



---

## Index

1	Introduction.....	4
2	Sampling .....	4
3	Quality requirements.....	5
4	Results of the sampling and evaluation.....	7
4.1	Fatty Acid Methyl Ester Content .....	8
4.2	Density at 15 °C .....	9
4.3	Sulfur Content .....	10
4.4	Water Content.....	12
4.5	Total Contamination.....	14
4.6	Oxidation Stability .....	15
4.7	Acid Number.....	17
4.8	Iodine Number .....	18
4.9	Mono-, di- and triglycerides, total glycerol and free glycerol .....	19
4.10	Alkaline Metals (Sodium + Potassium) and Alkaline Earth Metals (Calcium + Magnesium). 22	
4.11	Phosphorous Content.....	24
4.12	Content of Linolenic Acid Methyl Ester.....	25
4.13	Cold Filter Plugging Point (CFPP) .....	26
4.14	Cloud point (CP).....	28
	Additional Campaigns .....	30
5	Summary.....	31
6	Annex.....	33
6.1	Limits and Test Methods .....	33



---

## List of figures

Figure 1: Fatty Acid Methyl Ester Content acc. to DIN EN 14103. ....	8
Figure 2: Density at 15 °C acc. to DIN EN ISO 12185. ....	9
Figure 3: Sulfur content acc. to DIN EN ISO 20846. ....	10
Figure 4: Sulfur content of blend components for biodiesel acc. to DIN EN ISO 20846. ....	11
Figure 5: Water content acc. DIN EN ISO 12937. ....	12
Figure 6: Water content according to DIN EN ISO 12937 of the warehouse operators. ....	13
Figure 7: Total contamination acc. to DIN EN 12662. ....	14
Figure 8: Oxidation stability acc. to DIN EN 14112. ....	16
Figure 9: Acid Number acc. to DIN EN 14104. ....	17
Figure 10: Iodine number acc. to DIN EN 16300. ....	18
Figure 11: Monoglycerides content acc. to DIN EN 14105. ....	20
Figure 12: Diglycerides content acc. to DIN EN 14105. ....	20
Figure 13: Triglycerides content acc. to DIN EN 14105. ....	21
Figure 14: Total glycerol content acc. to DIN EN 14105. ....	21
Figure 15: Free glycerol content acc. to DIN EN 14105. ....	22
Figure 16: Sum of alkali metals Sodium and Potassium acc. to DIN EN 14538. ....	23
Figure 17: Sum of alkaline earth metals Calcium and Magnesium acc. to DIN EN 14538. ....	23
Figure 18: Phosphorus content acc. to DIN EN 14107. ....	24
Figure 19: Content of Linolenic Acid Methyl Ester acc. to DIN EN 14103. ....	25
Figure 20: CFPP acc. to DIN EN 116. ....	27
Figure 21: CFPP of blend components for biodiesel acc. to DIN EN 116. ....	27
Figure 22: Cloud point acc. to DIN EN 23015. ....	28
Figure 23: Cloud point of blend components for biodiesel acc. to DIN EN 23015. ....	29
Figure 24: Comparison of the number of samples for the years 2022 and 2023. ....	31



---

## 1 Introduction

In order to achieve the EU's goal of becoming climate neutral by 2050, an immediate switch to climate-friendly fuels and the use of all available options is essential. One of these options is the use of biofuels in the transport sector to drive forward the decarbonisation of road, ship and air transport. According to the BLE report, the total reduction in greenhouse gas emissions from all biofuels in Germany in 2022 was around 87%. The largest share is attributable to the use of biodiesel (FAME).

Therefore, biodiesel is the most important biofuel in Germany and in the entire European Union. Biodiesel is mainly used as an additive to diesel fuel to reduce CO<sub>2</sub> emissions and the consumption of fossil fuels. In Germany, blends of up to 10% (B10) may be offered at public petrol stations from May 2024. The European standard EN 14214 describes the requirements that biodiesel must fulfil in order to be placed on the market as a pure fuel or blend component. The Association Quality Management Biodiesel (AGQM), founded in 1999 by German biodiesel producers and traders, promotes and monitors the biodiesel quality in Germany and Austria.

As a measure of quality assurance, AGQM carries out unannounced sampling of its members at least three times a year in order to determine and check the actual product quality under real operating conditions at the manufacturers' and warehouse operators' sites. This quality report summarises the results of these demanding sampling campaigns from the year 2023.

## 2 Sampling

The Quality Management system (QM system) of the AGQM stipulates that unannounced sampling is carried out on the members at least three times a year. Since 2017, all members who are found to have an irregularity (violation of a limit or acceptance limit) in one of the three main campaigns have to participate in an additional campaign that follows the respective main campaign and is also unannounced.

Sampling and analysis are performed by an independent laboratory accredited for biodiesel analysis. In 2023, samples were taken at 16 production sites and three warehouse operators. A campaign was carried out in each of the winter, intermediate and summer periods to take into account the regulations of the national Annex NB of DIN EN 14214 for the limit values of the parameters cloud point and CFPP. Each member state can set these limit values individually, as climatic conditions differ greatly in some cases.



---

Campaign 1:	06. February to 17. February	Winter grade
Campaign 2:	12. June to 23. June	Summer grade
Campaign 3:	23. October to 03. November	Intermediate grade

A total of 57 samples were taken and analysed in the main campaigns and 5 samples in the necessary additional campaigns. For each sampling, one analytical sample, one sample as a potential arbitration sample and one sample that remains with the producer or warehouse operator as a reserve sample are taken.

The analysis results are evaluated by the AGQM office, and the member companies are subsequently informed about the result. If there are doubts about the results of the sampling, members can address AGQM to apply arbitration proceedings. The member assigns an independent laboratory accredited for biodiesel analytics. As arbitration sample one of the two samples taken during the sampling is used. The result of the arbitral analysis is binding for both sides. If a deviation is confirmed in the arbitral analysis, the member has to participate in the next unannounced additional campaign and further sanction measures may be initiated.

The implementation of the QM system of the AGQM is evaluated for each member based on a points system. Bonus points are awarded for participation in quality assurance measures and sanction points for violations of the QM system. The percentage ratio of sanction points to bonus points is used to assess the need for further measures.

### **3 Quality requirements**

According to the AGQM QM system, all quality parameters listed in the legal requirements of the 36<sup>th</sup> BImSchV (Federal Immission Control Ordinance) are examined during sampling to verify the biofuel properties.

The analyses are always based on the current version of DIN EN 14214. In 2023, the required standard limit values as well as the associated acceptance limit values corresponded to DIN EN 14214:2012+A2:2019. For the parameters water content, total contamination and cold filter plugging point (CFPP), AGQM sets higher demands on the biodiesel quality of its members than required by legislative authority. Separate limit values for warehouse operators were also defined in the AGQM guidelines for the parameter water content and for the parameter total contamination the AGQM limit value also corresponds to the AGQM acceptance limit value.



---

Table 1 lists the parameters to be tested with their limit values according to DIN EN 14214 and Table 2 lists the AGQM limit values for the corresponding parameters.

In addition, the market development of recent years shows that to improve the greenhouse gas balance and support the circular economy concept, alternative raw materials to produce biodiesel, e.g., used cooking oils, raw materials listed in Annex IX part A of the renewable energy directive as well as free fatty acids are used. Due to the nature of the raw materials, some of these products show quality differences compared to DIN EN 14214 and therefore cannot be used as a pure fuel, but only as a blending component for biodiesel from classic raw materials (e.g. rapeseed oil). Since manufacturers of biodiesel from alternative raw materials are also members of the AGQM, a separate chapter for blending components for biodiesel was implemented in the QM system. By blending such components with other goods, an overall standard-compliant biodiesel can be produced. Special limit values for blend components for biodiesel were included in the QM system for the parameters sulfur content, CFPP and cloud point. These three parameters are strongly determined by the fatty acid composition or impurities in the raw material and can hardly be influenced in the production process. If a producer applies to the AGQM for a corresponding exemption, the specific limit values (Table 3) for blend components for biodiesel are used for assessment instead of the values of DIN EN 14214 as the limit values to be complied with for the parameters sulfur content, CFPP and cloud point.

---

## 4 Results of the sampling and evaluation

In the following section, the results of the sampling at the AGQM member companies in the three main campaigns are presented graphically. The applicable limit values and acceptance limit values are listed for each parameter and the parameter is classified regarding the influence on the product quality.

The results presented in this report are anonymous and do not indicate the origin of the sample. The values in the charts are shown in ascending order for each campaign to show the distribution. The "Sample Number" axis shows how many samples were taken in each campaign.

The limits are indicated in the diagrams by an orange line, the acceptance limits by a red line. Under customs law, but also regarding the allocation of sanction points under the QM system, these acceptance limits are decisive. The acceptance limits can be calculated according to DIN EN ISO 4259-1 using the following formulas:

$$AL = L(\min) - (0.59 \cdot R) \quad \text{bzw.} \quad AL = L(\max) + (0.59 \cdot R)$$

With AL = acceptance limit; L = limit (from EN 14214); R = comparability (from standard method)

For example:

$$AL(\text{ester content}) = 96.5\% (m/m) - (0.59 \cdot 4.14\% (m/m)) = 94.0\% (m/m)$$

For some parameters, the 95 quantile is also given, which describes the value below or above which 95% of all results lie (excluding products with limit value violations and products for which special limit values apply).

## 4.1 Fatty Acid Methyl Ester Content

Test method:	DIN EN 14103:2011
Limit of DIN EN 14214:	min. 96.5% (m/m)
Acceptance limit:	min. 94.0% (m/m)

The fatty acid methyl ester content, or short ester content, provides information on the purity of the biodiesel. Depending on the nature of the raw material and the reaction conditions, by-products may be present in the final product which reduce the ester content. It is determined by gas chromatography and expressed as the sum of all fatty acid methyl esters of C6:0 to C24:1 in mass per cent % (m/m). EN 14214 requires an ester content of at least 96.5% (m/m). A distilled product after the transesterification usually has a higher ester content since undesirable substances can be separated in this way. According to DIN EN 14103, determined ester contents that are greater than 99.0% (m/m) are indicated with > 99.0% (m/m) as the result.

Figure 1 shows that all 57 samples comply with the standard limit of 96.5 % (m/m). Three samples per campaign had an ester content of 99.0% (m/m). The 95% quantile is 96.9% (m/m).

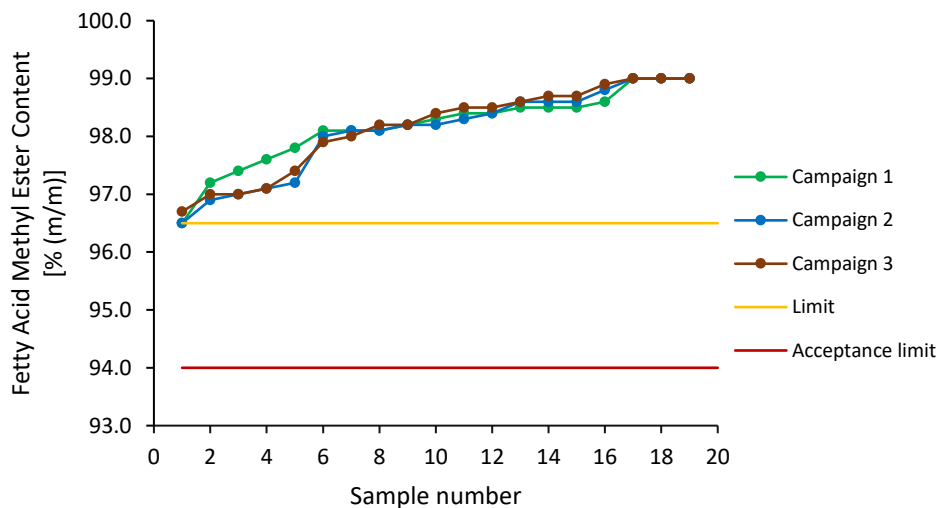


Figure 1: Fatty Acid Methyl Ester Content acc. to DIN EN 14103.



## 4.2 Density at 15 °C

Test method:	DIN EN ISO 12185:1996
Limit of DIN EN 14214:	min. 860 kg/m <sup>3</sup> and max. 900 kg/m <sup>3</sup>
Acceptance limit:	min. 859.7 kg/m <sup>3</sup> and max. 900.3 kg/m <sup>3</sup>

The density of a substance is the quotient of its mass and its volume at a specified temperature. According to DIN EN 14214, the density of biodiesel at 15 °C must be between 860-900 kg/m<sup>3</sup>. Both the FAME composition and the purity of the biodiesel have an influence on the density. For example, an increased methanol content lowers the density.

Figure 2 shows the density of the analysed samples. All samples comply with the density range required by the standard. Almost all samples are in a very narrow range between 881 kg/m<sup>3</sup> and 883 kg/m<sup>3</sup>, which indicates the main use of rapeseed oil as feedstock. Lower densities of approx. 875 kg/m<sup>3</sup> are due to the use of other raw materials. It can also be stated that the densities of the samples are not subject to seasonal fluctuations and can be regarded as almost constant within a year.

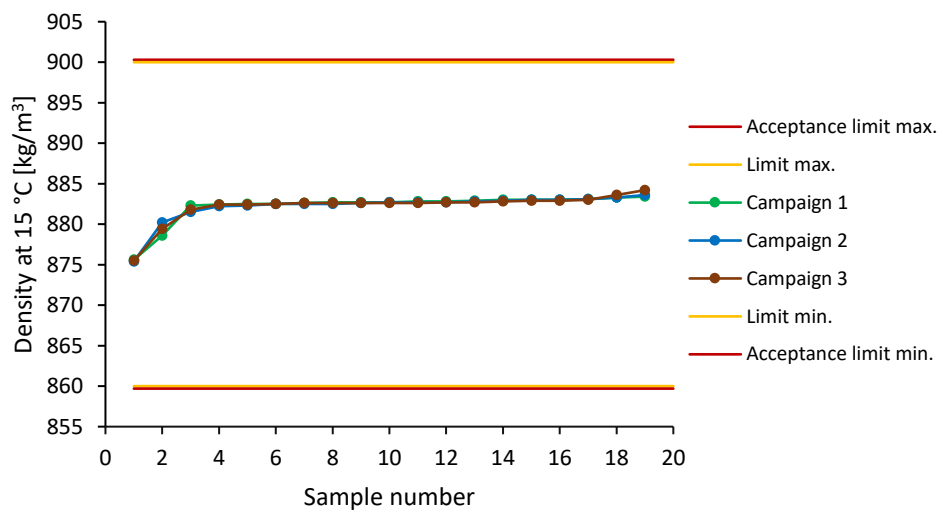


Figure 2: Density at 15 °C acc. to DIN EN ISO 12185.

### 4.3 Sulfur Content

Test method:	DIN EN ISO 20846:2011
Limit of DIN EN 14214:	max. 10.0 mg/kg
Acceptance limit:	max. 11.3 mg/kg
AGQM limit for blend components for biodiesel:	max. 20.0 mg/kg

The AGQM limit value for sulphur content is equal to the AGQM acceptance limit value.

Sulfur can already be contained in the raw materials used for biodiesel production. In plants that can take up sulfur compounds during growth, the sulfur content is usually between 2 mg/kg and 7 mg/kg. Animal fats and used cooking oils can contain sulfur in the form of protein compounds, resulting in a sulfur content of up to 30 mg/kg. Depending on the type of sulfur compound, the content in the biodiesel can be reduced by washing processes or distillation of the biodiesel.

As can be seen in Figure 3, the required limits are met by all samples. In campaign 1, as many as 14 of the samples analysed had a sulfur content of less than 4 mg/kg. The 95% quantile is 8.2 mg/kg.

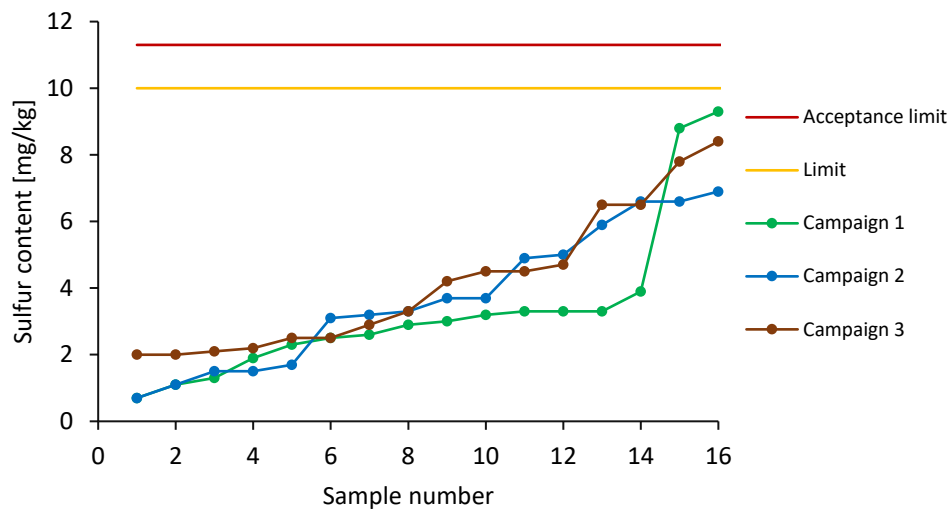


Figure 3: Sulfur content acc. to DIN EN ISO 20846.

Figure 4 shows the analytical results of the samples of those companies that have made use of the exemption for blending components for biodiesel.

In order to take into account current market requirements and raw material offers, the AGQM limit value for the sulfur content for blend components for biodiesel has been raised to a maximum of 20 mg/kg. The limit value has also been defined as an acceptance limit value. All samples of blend components for biodiesel were below the limit value of 20 mg/kg. Six of the nine samples comply with the DIN EN 14214 limit value of 10 mg/kg.

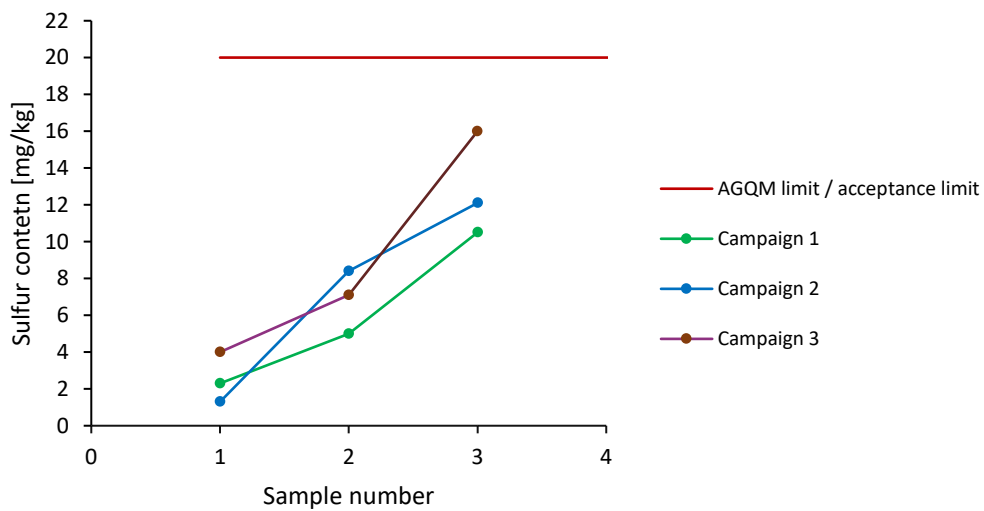


Figure 4: Sulfur content of blend components for biodiesel acc. to DIN EN ISO 20846.

## 4.4 Water Content

Test method:	DIN EN ISO 12937:2002
Limit of DIN EN 14214:	max. 0.050 % (m/m)
AGQM limit (producers):	max. 0.027 % (m/m)
Acceptance limit (producers):	max. 0.034 % (m/m)
AGQM limit (warehouse operators):	max. 0.032 % (m/m)
Acceptance limit (warehouse operators):	max. 0.039 % (m/m)

Biodiesel can physically dissolve up to 0.0150 % (m/m). Since almost all production processes include a water wash, the product needs to be dried at the end of the biodiesel production. Subsequently, the storage conditions must be selected accordingly to avoid a renewed contamination of the biodiesel by atmospheric moisture.

Fossil diesel fuels can only absorb very small amounts of water, so dissolved water could precipitate when mixed with biodiesel that significantly exceeds the water limit. Free water can cause corrosion or promote microbial growth. DIN EN 14214 requires a maximum water content of 0.050 % (m/m). Due to the problems described above, AGQM has set stricter requirements with a maximum water content of 0.027 % (m/m) for producers and 0.032 % (m/m) for warehouse operators.

Figure 5 shows the values for the water content. All samples tested are well below the standard limit. An exceedance of the AGQM limit value occurred in four cases.

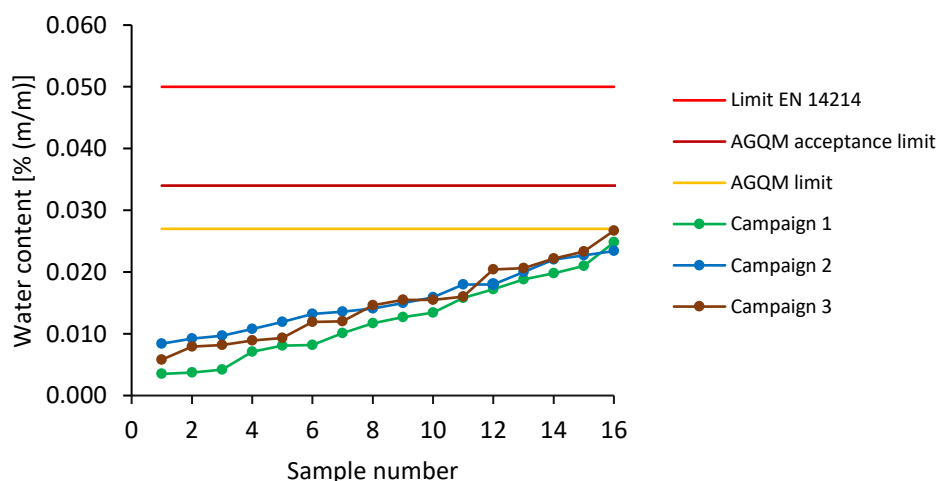


Figure 5: Water content acc. DIN EN ISO 12937.

Figure 6 plots the results for the water content of the warehouse operators. All samples comply with the specific AGQM limit of 0.032 % (m/m).

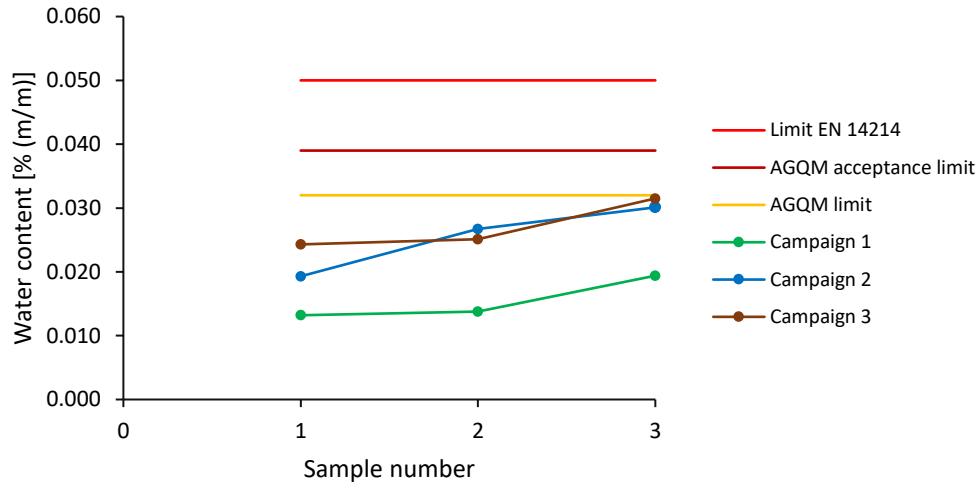


Figure 6: Water content according to DIN EN ISO 12937 of the warehouse operators.

## 4.5 Total Contamination

Test method: *DIN EN 12662:1998*

Limit of DIN EN 14214: *max. 24 mg/kg*

AGQM limit: *max. 20 mg/kg*

*The AGQM limit value for total contamination is equal to the AGQM acceptance limit value.*

The total contamination is a measure of the content of non-soluble particles ("rust and dust"). The determination is carried out after filtration of a heated sample gravimetrically by weighing the filter. Biodiesel is normally not distilled, which is why total contamination is an important quality feature. High levels of insoluble particles can lead to filter blockages and injector wear. The AGQM has set its own stricter limit of 20 mg/kg to account for this issue and the relatively poor precision of the method. The limit value has also been defined as an acceptance limit value.

Figure 7 shows that, except for one sample, all other samples complied with the stricter AGQM limit for total contamination and the 95% quantile was 14 mg/kg.

The member whose sample in campaign 1 had a total contamination level of 22 mg/kg, exceeding AGQM's own acceptance limit, received one sanction point.

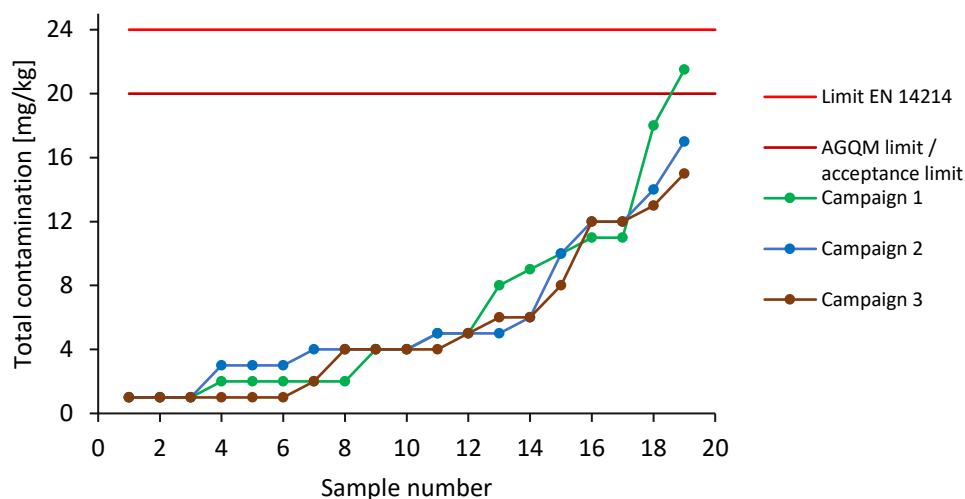


Figure 7: Total contamination acc. to DIN EN 12662.

---

## 4.6 Oxidation Stability

<i>Test method:</i>	<i>DIN EN 14112:2016</i>
<i>Limit of DIN EN 14214:</i>	<i>min. 8.0 h</i>
<i>Acceptance limit:</i>	<i>min. 6.6 h</i>

Oxidation stability is a measure of the resistance of a fuel to oxidative processes. Vegetable oils and biodiesel produced from them contain natural antioxidants (e.g., tocopherols) that slow down the ageing process. Synthetic stabilizers are also used. Once a year, AGQM tests products that can be used to increase the oxidation stability of biodiesel at the request of interested additive manufacturers. Additives that pass the test are included in the AGQM no-harm list. A free copy of the list can be ordered from the AGQM website.

The test method for the oxidation stability of biodiesel is the so-called Rancimat test. At 110 °C, a constant flow of air is passed through the sample to be tested. After the oxidation reserve (natural reserve and additives) of the sample is degraded, volatile oxidation products are formed, which are conducted together with the air into the test liquid of the measuring cell and increase the conductivity there. The time until the detection of these oxidation products is called induction time or oxidation stability. DIN EN 14214 requires a minimum oxidation stability of 8.0 hours.

Figure 8 shows the oxidation stabilities of the samples tested. In campaign 2, there were underruns of the standard limit value within the acceptance limit value of two samples with oxidation stabilities of 7.7 h and 6.9 h. In campaign 3, one of the samples fell below the standard limit outside the acceptance limit with an oxidation stability of 5.2 hours. The value was the result of an arbitration analysis carried out, meaning that a sanction point had to be awarded to the member. In its statement, the member declared that it would monitor the parameter more closely in the near future. There were no further anomalies in the additional campaign that followed.

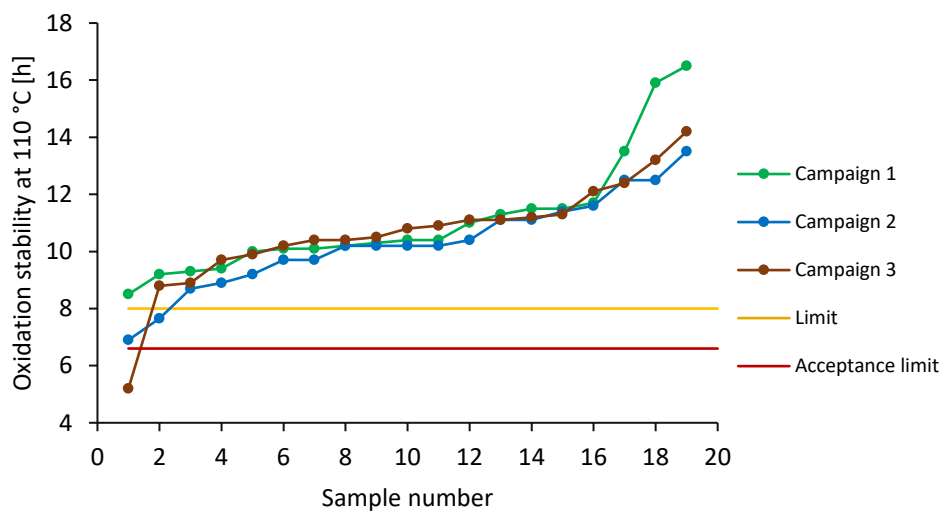


Figure 8: Oxidation stability acc. to DIN EN 14112.



## 4.7 Acid Number

Test method:	DIN EN 14104:2003
Limit of DIN EN 14214:	max. 0.50 mg KOH/g
Acceptance limit:	max. 0.54 mg KOH/g

The acid number is a measure of free acids (especially fatty acids) in the product. Fatty acids are weak acids and therefore only slightly corrosive. In the production process, small residues of soaps are cleaved usually by neutralization with inorganic acids. The resulting free fatty acids can remain in the biodiesel. The acid number can also increase during storage of FAME, as aging processes to ester cleavage or the formation of short-chain carboxylic acids. Under typical storage conditions, however, this effect is hardly observed. DIN EN 14214 requires an acid value of no more than 0.50 mg KOH/g.

Figure 9 shows the measured values for the acid value. All samples comply with the standard limit of 0.50 mg KOH/g.

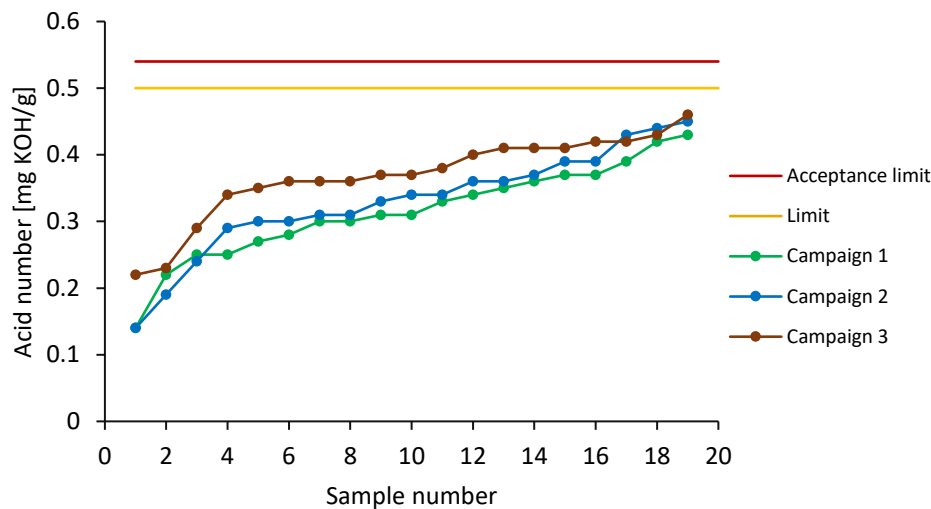


Figure 9: Acid Number acc. to DIN EN 14104.

## 4.8 Iodine Number

Test method:	DIN EN 16300:2012
Limit of DIN EN 14214:	max. 120 g Iodine/100 g
Acceptance limit:	max. 124 g Iodine/100 g

The iodine number is a measure of the proportion of double bonds which is present in fatty acid methyl ester. It varies with the type of raw material used. Since unsaturated fatty acids are more prone to oxidation reactions, the stability of biodiesel decreases with increasing number of double bonds, i.e., increasing iodine number. Therefore, the iodine number, in addition to the oxidation stability, is an indicator of the stability of biodiesel.

For determination, two different methods are specified in DIN EN 14214. In the AGQM sampling campaigns, the iodine number is calculated from the fatty acid profile measured by gas chromatography in accordance with DIN EN 16300. The result is given in g iodine/100 g biodiesel. Figure 10 shows the results for the iodine value. All samples analysed are below the standard limit and show an almost identical course within the three campaigns carried out, which overall indicates a constant raw material use over the year.

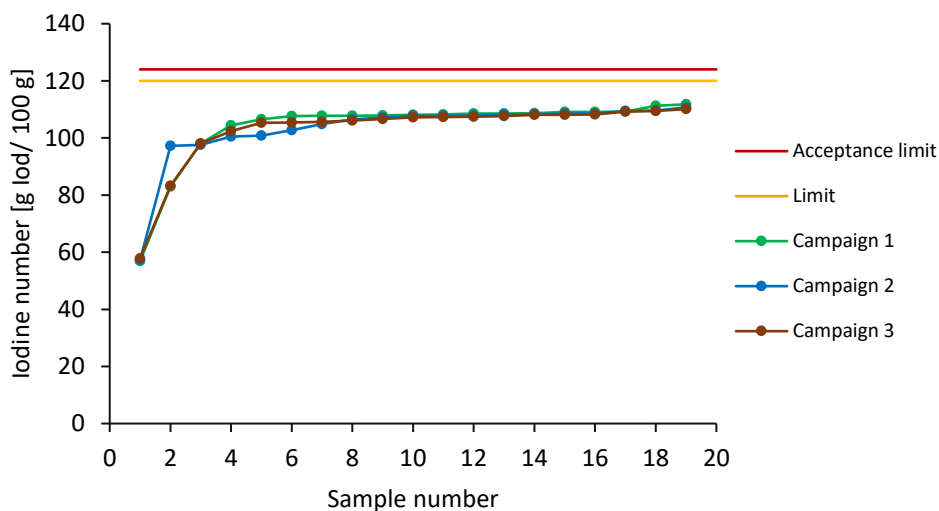


Figure 10: Iodine number acc. to DIN EN 16300.

#### 4.9 Mono-, di- and triglycerides, total glycerol and free glycerol

*Test method:* DIN EN 14105:2011

Monoglycerides

*Limit of DIN EN 14214:* max. 0.70% (m/m)

*Acceptance limit:* max. 0.82% (m/m)

Diglycerides

*Limit of DIN EN 14214:* max. 0.20% (m/m)

*Acceptance limit:* max. 0.24% (m/m)

Triglycerides

*Limit of DIN EN 14214:* max. 0.20% (m/m)

*Acceptance limit:* max. 0.27% (m/m)

Total glycerol

*Limit of DIN EN 14214:* max. 0.25% (m/m)

*Acceptance limit:* max. 0.28% (m/m)

Free glycerol

*Limit of DIN EN 14214:* max. 0.020% (m/m)

*Acceptance limit:* max. 0.026% (m/m)

In the transesterification of vegetable oils with methanol, in addition to the main product (fatty acid methyl ester) also different levels of by-products like mono- and diglycerides, free glycerol occur. Furthermore, unreacted vegetable oil (triglycerides) is found in the reaction mixture. Since glycerol is virtually insoluble in biodiesel, it can be separated almost completely by decanting and subsequent water washing. The ratio of the content of mono-, di- and triglycerides is a measure of the completeness of the transesterification reaction since the concentration usually increases in the order triglycerides < diglycerides < monoglycerides. The cleavage of the last fatty acid residue is the slowest step of the reaction, therefore the standard limit for monoglycerides is slightly higher at 0.70% (m/m) than that for di- and triglycerides at 0.20% (m/m). The content of mono-, di- and triglycerides can only be reduced to a certain degree. The almost complete removal of the glycerides is possible only by distillation.

Figure 11 to Figure 13 show the results of the analyses for the content of mono-, di- and triglycerides. There was only one exceedance of the limit value within the acceptance limit for the content of triglycerides in one sample in campaign 2. All other samples comply with the corresponding DIN limits

for mono-, di- and triglycerides. Some samples show values  $< 0.15$  % (m/m) for the monoglyceride content, which indicates that the production process includes a distillation step.

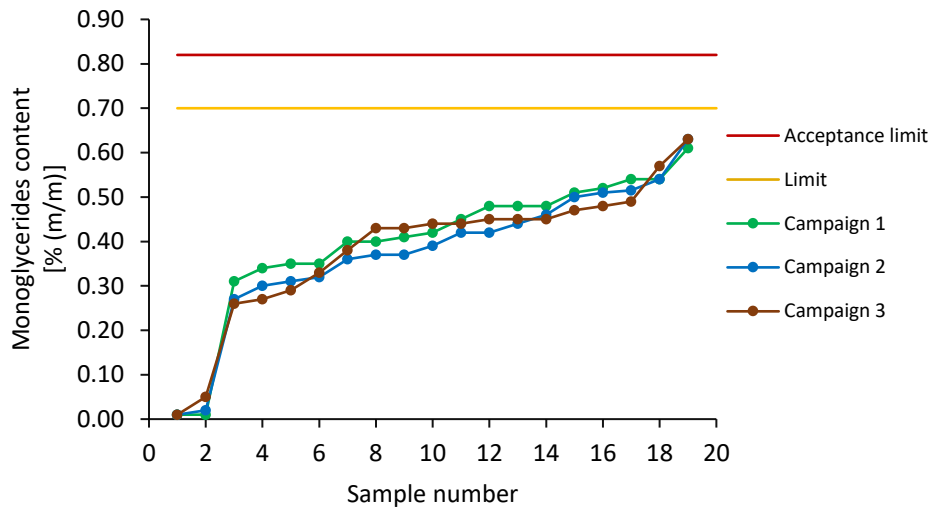


Figure 11: Monoglycerides content acc. to DIN EN 14105.

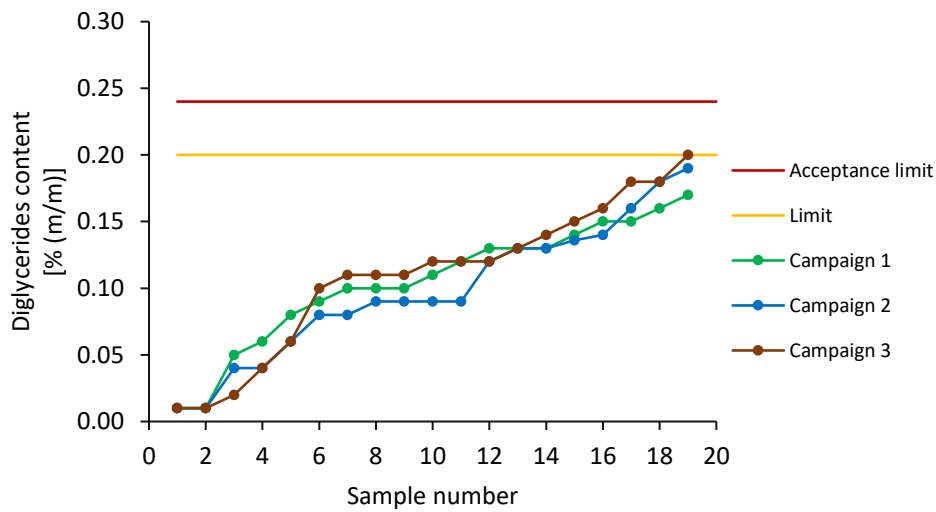


Figure 12: Diglycerides content acc. to DIN EN 14105.

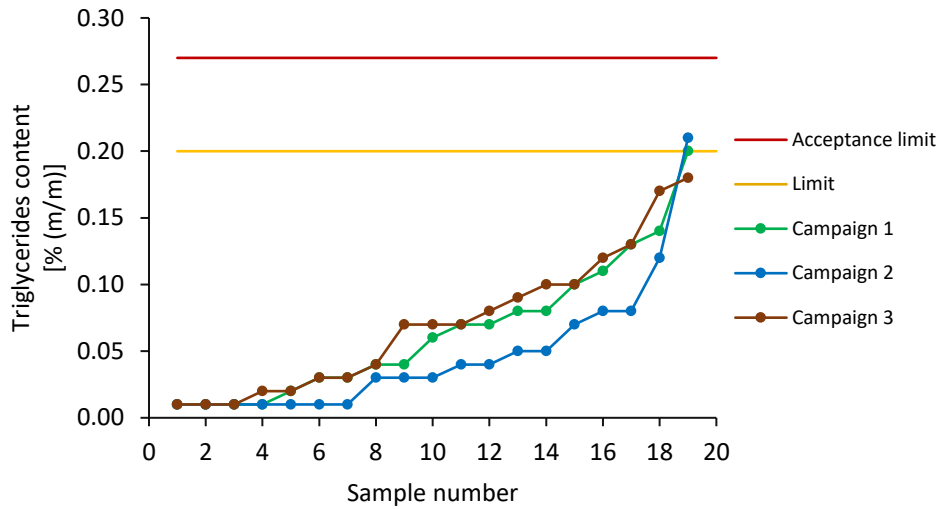


Figure 13: Triglycerides content acc. to DIN EN 14105.

The total glycerol content is shown in Figure 14. All samples analysed comply with the standard limit of 0.25% (m/m).

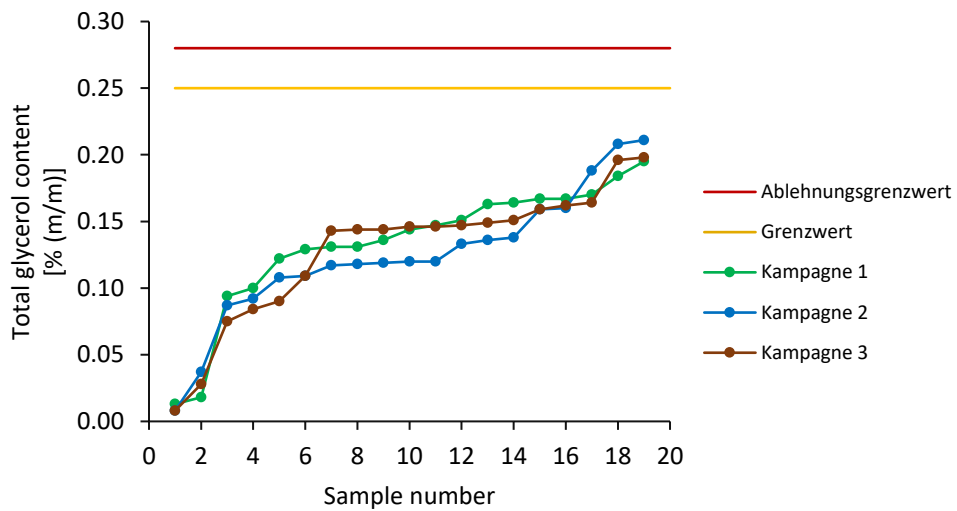


Figure 14: Total glycerol content acc. to DIN EN 14105.

Figure 15 shows the free glycerol content. One sample in campaign 2 exceeded the standard limit within the acceptance limit with a free glycerol content of 0.024 % (m/m). This was the sample that also exceeded the limit value for the triglyceride content. All other samples showed no abnormalities.

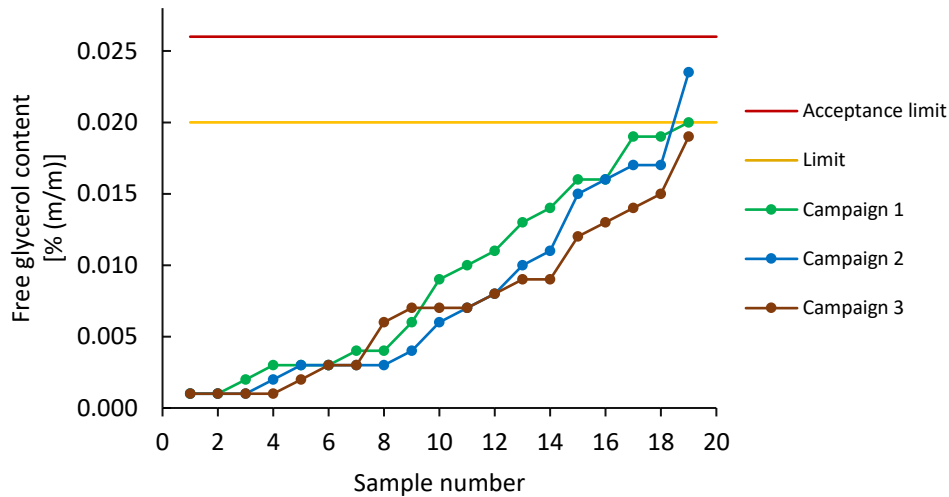


Figure 15: Free glycerol content acc. to DIN EN 14105.

#### 4.10 Alkaline Metals (Sodium + Potassium) and Alkaline Earth Metals (Calcium + Magnesium)

Test method: *DIN EN 14538:2006*  
 Limit of DIN EN 14214: *max. 5.0 mg/kg (sum parameter)*  
 Acceptance limit: *max. 6.1 mg/kg (sum parameter)*

In biodiesel production, sodium and potassium methanolates are usually used as catalysts. If residues of these are not completely removed in the wash, residues of the cations in the biodiesel are usually present in the form of soaps. Soaps can lead to filter blockages, deposits in injection pumps and nozzle needles and ash formation.

The alkaline earth metals calcium and magnesium are either added to the raw material in the process or can reach the product through the use of tap water for water washing during the production process. The reaction with free fatty acids produces calcium and magnesium soaps that are more voluminous than alkaline metal soaps.

Figure 16 and Figure 17 clearly show that biodiesel producers attach great importance to low levels of alkaline and alkaline earth metals. The 95% quantile for the sodium and potassium content is 1.7 mg/kg.

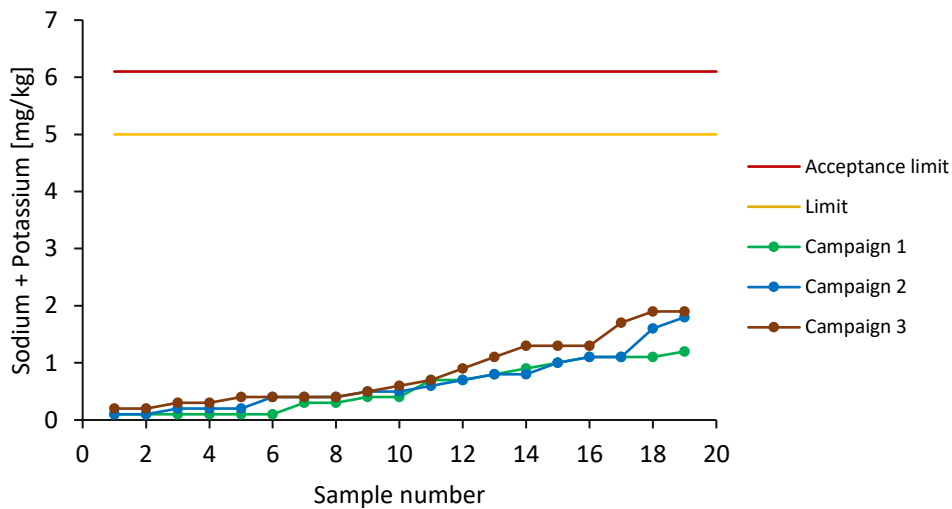


Figure 16: Sum of alkali metals Sodium and Potassium acc. to DIN EN 14538.

The content of the alkaline earth metals magnesium and calcium (Figure 17) is mostly below the determination limit of 0.1 mg/kg. The 95% quantile is only 0.3 mg/kg.

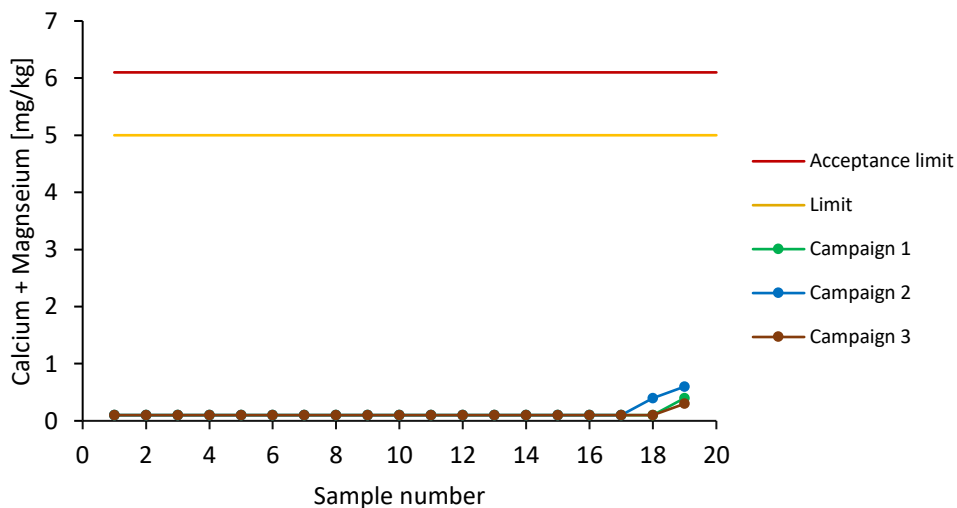


Figure 17: Sum of alkaline earth metals Calcium and Magnesium acc. to DIN EN 14538.

## 4.11 Phosphorous Content

<i>Test method:</i>	<i>DIN EN 14107:2003</i>
<i>Limit of DIN EN 14214:</i>	<i>max. 4.0 mg/kg</i>
<i>Acceptance limit:</i>	<i>max. 4.5 mg/kg</i>

The phosphorus content must already be considered during the selection of raw materials or reduced by a refining process before transesterification. Vegetable oils and animal fats contain phosphorus in form of phospholipids. These can hinder the transesterification process since they act as emulsifiers and thus disrupt the phase separation. Phosphorus can also enter the biodiesel during production if phosphoric acid is used to break down the soaps, but it is usually easy to remove with water. Since phosphorus is a catalyst poison, it can affect the effect of exhaust gas aftertreatment systems. The parameter is to be included in EN 14538 in 2024.

Figure 18 shows the values for the phosphorus content. All samples are well below the standard limit of 4.0 mg/kg. The 95% quantile of the values is 0.9 mg/kg.

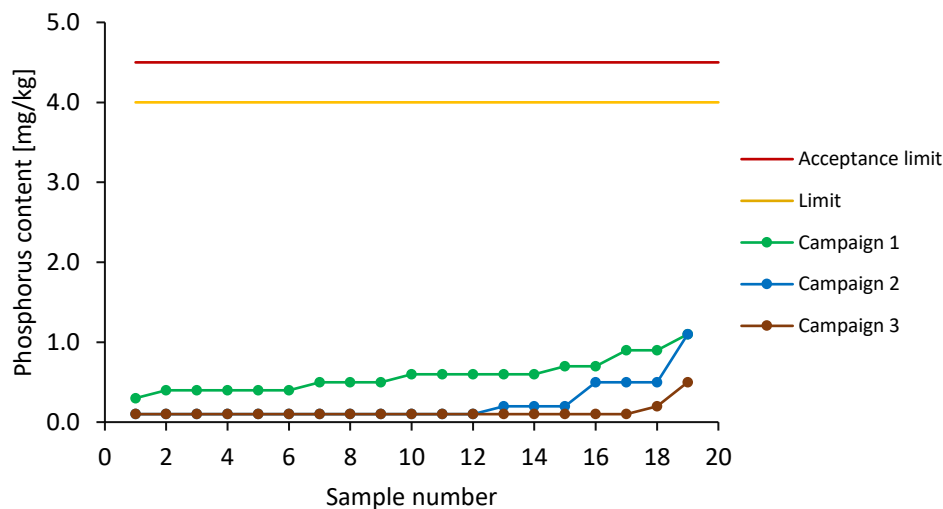


Figure 18: Phosphorus content acc. to DIN EN 14107.



## 4.12 Content of Linolenic Acid Methyl Ester

Test method:	DIN EN 14103:2015
Limit of DIN EN 14214:	max. 12.0% (m/m)
Acceptance limit:	max. 14.9% (m/m)

Linolenic acid is a triple unsaturated fatty acid with 18 carbon atoms (C18:3). Due to its chemical structure, it is extremely prone to oxidative attacks, which is why the content of linolenic acid methyl ester in biodiesel is limited to 12% (m/m). This is determined from the fatty acid profile by using gas chromatography.

Figure 19 shows that all samples analysed have a linolenic acid methyl ester content within the requirements of the standard. The linolenic acid content of pure rapeseed oil is usually between 7% and 10%. The lower contents in a large part of the samples show that the raw material rapeseed oil often used in biodiesel production was at least partially replaced by other oils in the summer campaign (campaign 2). In two samples, the content of linolenic acid methyl ester is even below 2% (m/m) throughout the year.

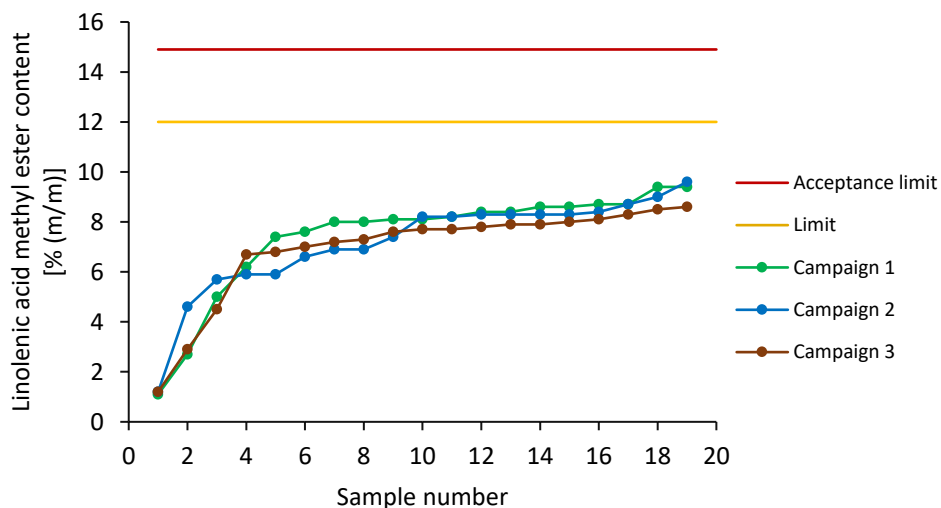


Figure 19: Content of Linolenic Acid Methyl Ester acc. to DIN EN 14103.



### 4.13 Cold Filter Plugging Point (CFPP)

*Test method:* DIN EN 116:2015

*Limits according to DIN EN 14214 for biodiesel as blend component in diesel fuel:*

<i>Period</i>	<i>Limit</i>	<i>Acceptance limit</i>	
<i>from 15.04. to 30.09.</i>	<i>0 °C</i>	<i>+1.5 °C</i>	<i>Summer period</i>
<i>from 01.10. to 15.11.</i>	<i>-5 °C</i>	<i>-3.2 °C</i>	<i>Intermediate period</i>
<i>from 16.11. to 28./29.02.</i>	<i>-10 °C</i>	<i>-7.9 °C</i>	<i>Winter period</i>
<i>from 01.03. to 14.04.</i>	<i>-5 °C</i>	<i>-3.2 °C</i>	<i>Intermediate period</i>
<i>AGQM limit for blend components for biodiesel</i>	<i>+10 °C</i>	<i>+11.4 °C</i>	<i>All year</i>

The CFPP is a measure of the filterability of biodiesel at low temperatures. The requirements for "cold resistance" are regulated nationally depending on the prevailing climatic conditions resulting in different requirements for summer, intermediate and winter quality.

In Germany, regarding the cold properties, the legal regulation applies that biodiesel as a blend component for diesel fuel must comply with a CFPP of -10 °C between 16.11. and the 28./29.02. as long as the -20 °C required in DIN EN 14214 can be achieved by additivation. In Germany, the additives are then usually used in the refineries of the mineral oil companies for the blends of diesel fuel and biodiesel. Once a year, AGQM tests flow improvers that can be used to lower the CFPP of biodiesel at the request of interested additive manufacturers. Additives that pass the test are included in the AGQM No-Harm List. A free copy of the list can be ordered from the AGQM website.

Figure 20 shows the measured values and various limit values for the CFPP. The winter limits and campaign 1 are shown in green, the summer limits and campaign 2 in blue and the intermediate period with campaign 3 in red.

All samples tested comply with the specific seasonal limits.

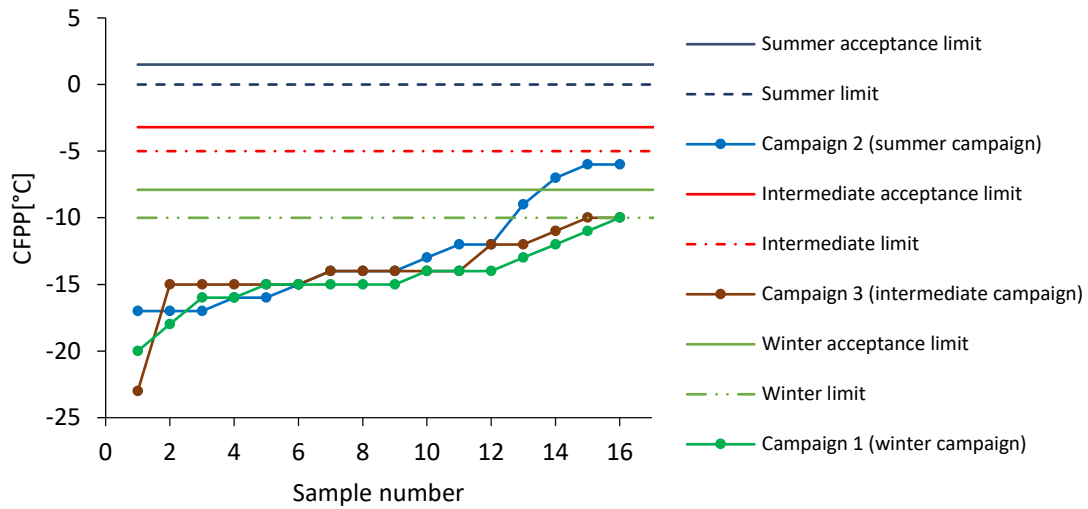


Figure 20: CFPP acc. to DIN EN 116.

Figure 21 shows the measured values of the members for the CFPP that make use of the exemption for blend components for biodiesel according to QM system section 2.1.1. For this case, an AGQM limit value of +10 °C, which applies all year round, was set. All samples analysed comply with the AGQM limit value.

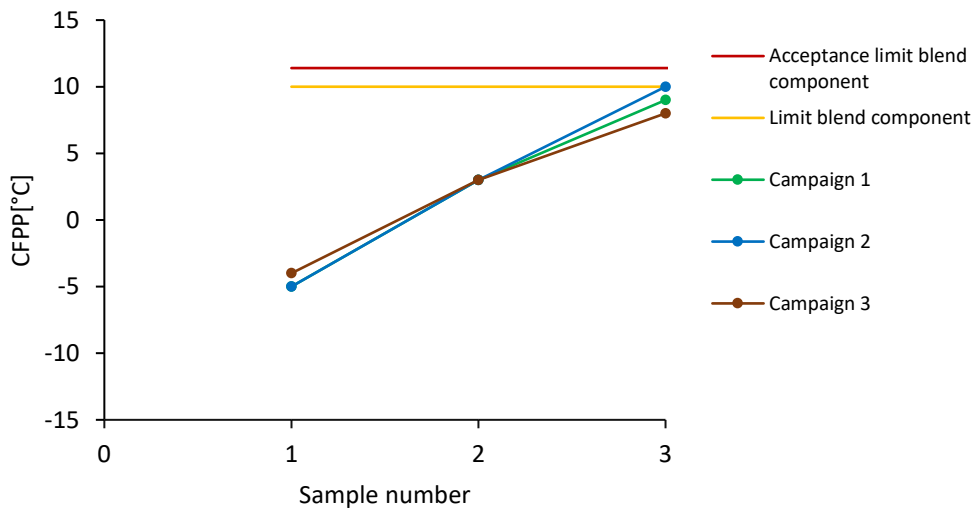


Figure 21: CFPP of blend components for biodiesel acc. to DIN EN 116.

#### 4.14 Cloud point (CP)

Test method: *DIN EN 23015:1994*

Limit according to *DIN EN 14214* for biodiesel as blend component in diesel fuel:

Period	Limit	Acceptance limit	
from 15.04. to 30.09.	5 °C	7.4 °C	Summer period
from 01.10. to 15.11.	0 °C	2.4 °C	Intermediate period
from 16.11. to 28./29.02.	-3 °C	-0.6 °C	Winter period
from 01.03. to 14.04.	0 °C	2.4 °C	Intermediate period
AGQM limit for blend components for biodiesel	+15 °C	+17.4 °C	All year

The cloud point is the temperature at which the first temperature-related turbidities ("clouds") form in a clear, liquid product when it cools under specified test conditions.

All samples investigated comply with the specific, seasonal limit values.

Figure 22 shows the measured values for the cloud point. The winter limit values and the corresponding results of main campaign 1 are shown in green, the summer limit values and the results of main campaign 2 in blue and the limit values of the transition period and the results of main campaign 3 in red.

All samples analysed comply with the specific, seasonal limits.

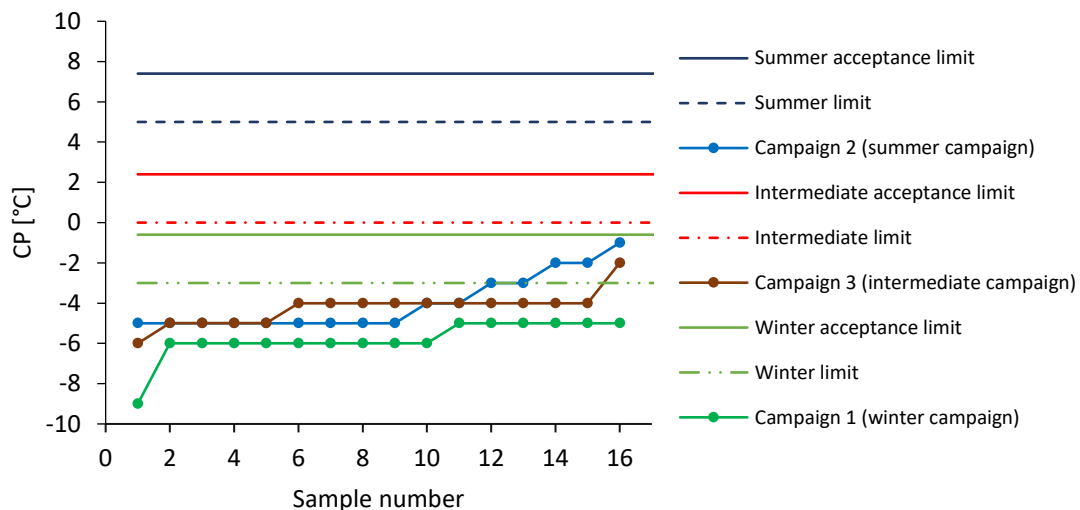


Figure 22: Cloud point acc. to DIN EN 23015.

As with the CFPP, separate limits apply to the cloud point for manufacturers of blend components for biodiesel.

In Figure 23, the measured cloud points are shown for the products of those members which make use of the exemption for blend components for biodiesel. The analysed samples of the blend components for biodiesel are all below the year-round specific limit of +15 °C.

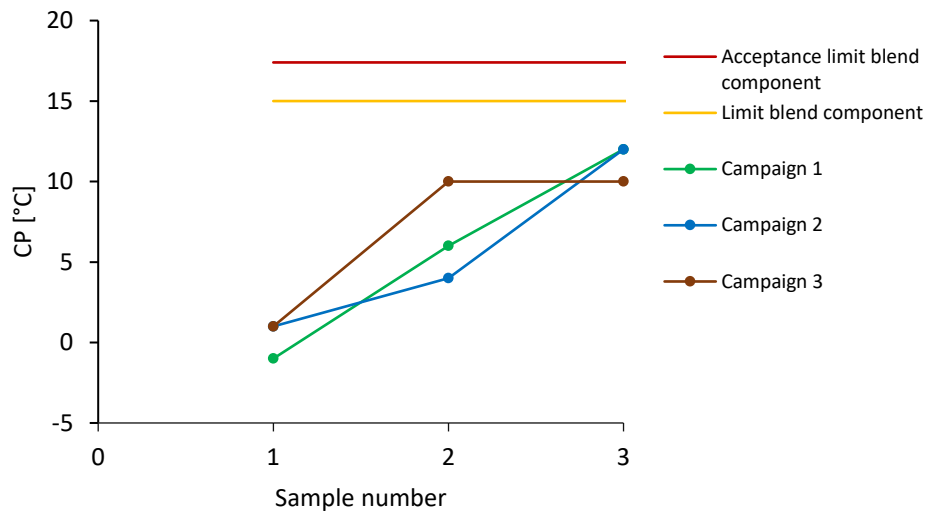


Figure 23: Cloud point of blend components for biodiesel acc. to DIN EN 23015.



---

## Additional Campaigns

Members who showed irregularities during a main campaign (violation of limit value or acceptance limit value) must subsequently participate in an additional campaign, which is also unannounced. In 2023, a total of three additional campaigns with five samples were carried out.

The periods of the additional sampling were:

Additional campaign 1:	20 March to 31 March	Interim period
Additional campaign 2:	07 August to 18 August	Summer period
Additional campaign 3:	04 December to 15 December	Winter period


One company was re-sampled in each of the additional campaigns 1 and 3. A total of three companies had to participate in the additional campaign 2. All companies sampled again showed no further abnormalities in the respective additional campaign.

## 5 Summary

Since 2010, AGQM has published an annual report on the quality of the biodiesel produced and traded by its members. In this report, the results of the unannounced sampling of the year 2023 are presented.

A comparison of the sample numbers for 2022 and 2023 (Figure 24) shows that the total number of samples analysed in 2023 (62) was four samples lower than in 2022. This is because the number of additional campaigns required was lower due to fewer limit violations. The number of limit violations within the corresponding rejection limits fell by a third to four violations. The number of rejection limit violations was also reduced by a third. Once again, one of the rejection limit violations involved an AGQM limit value being exceeded. This continues to show that the parameters for which stricter limits are required are precisely those that can be categorised as critical.

Overall, the 2023 reporting year was completed very well. Out of 1,254 inspection points, only 6 inspection points were conspicuous.

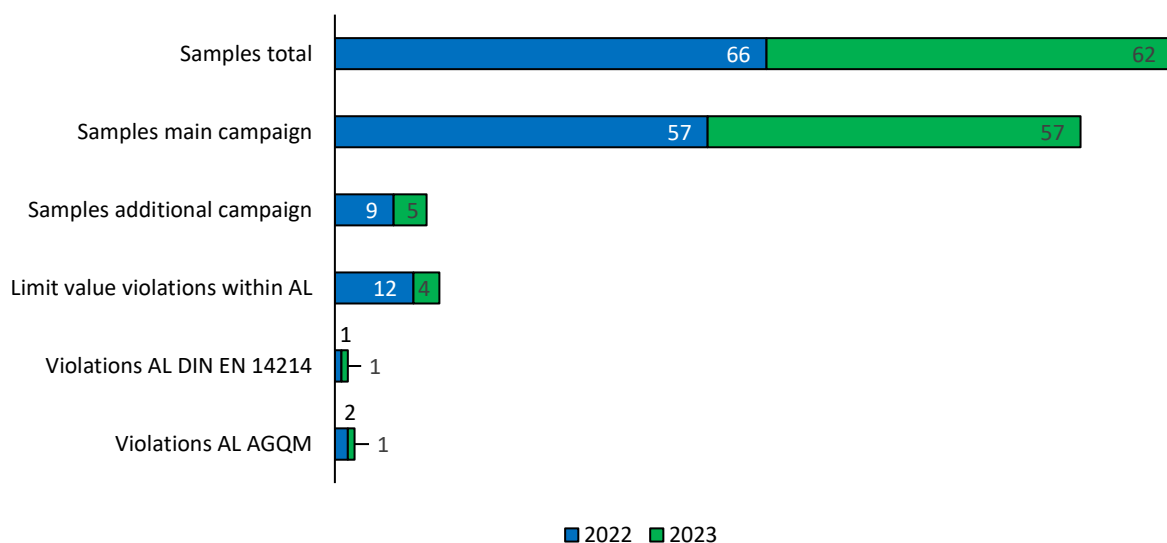

**Figure 24: Comparison of the number of samples for main and additional campaigns as well as the number of limit value violations within or violations of the rejection limit values (AL) for the years 2022 and 2023.**

The companies where abnormalities were detected during the sampling also detected the deviations within the scope of self-monitoring, so that it was possible to effectively prevent the goods from being placed on the market. In addition, with the support of the AGQM office, measures were taken to optimise the production process to avoid the occurrence of further limit value violations in the future.



---

The result shows that the unannounced sampling is an effective means of detecting anomalies and taking countermeasures as quickly as possible. In this way, the sampling intensively supports the member companies' own quality management as an independent control instrument. The AGQM supports all members with various support measures (e.g., audits or coaching) in root cause analysis and problem elimination. The FAME round robin test organised by AGQM in cooperation with DIN FAM, which is the world's most extensive, promotes continuous improvement and further development of the operating and analytical laboratories located at the member companies.

In this way, AGQM and its members make an important contribution to the stable and high-quality supply of biodiesel to the European fuel market. Labelling as AGQM goods thus represents a reliable mark of quality for customers and traders in the market.





## 6 Annex

### 6.1 Limits and Test Methods

Table 1: Limits and test methods for the parameters tested according to DIN EN 14214:2019.

Test Parameter	Method	Year of Publication	Unit	Standard Limits		Acceptance Limits	
				min.	max.	min.	max.
Fatty acid methyl ester content	DIN EN 14103	2011	% (m/m)	96.5	-	94.0	-
Density at 15 °C	DIN EN ISO 12185	1996	kg/m <sup>3</sup>	860	900	859.7	900.3
Sulfur content (UV)	DIN EN ISO 20846	2011	mg/kg	-	10.0	-	113
Water content K.-F.	DIN EN ISO 12937	2000	% (m/m)	-	0.050	-	0.059
Total contamination	DIN EN 12662	1998 <sup>1</sup>	mg/kg	-	24	-	28
Oxidation stability (at 110 °C)	DIN EN 14112	2016	h	8,0	-	6.6	-
Acid number	DIN EN 14104	2003	mg KOH/g	-	0.50	-	0.54
Iodine number	DIN EN 16300	2012	g Iodine/ 100 g	-	120	-	124.4
Content of linolenic acid methyl ester	DIN EN 14103	2011	% (m/m)	-	12.0	-	12.4
Content of free glycerol				-	0.02	-	0.026
Content of monoglycerides	DIN EN 14105	2011	% (m/m)	-	0.70	-	0.82
Content of diglycerides				-	0.20	-	0.24

<sup>1</sup> Due to the fact that the current version of DIN EN 12662 is not suitable for the determination of the total contamination of FAME, DIN EN 12662:1998 applies until further notice.



Test Parameter	Method	Year of Publication	Unit	Standard Limits		Acceptance Limits	
				min.	max.	min.	max.
Content of triglycerides	DIN EN 14105	2011	% (m/m)	-	0.20	-	0.27
Content of total glycerol				-	0.25	-	0.285
Content of alkali metals (Na+K)				-	5.0	-	6.1
Content of earth alkaline metals (Ca+Mg)	DIN EN 14538	2006	mg/kg	-	5.0	-	6.1
Phosphorous content	DIN EN 14107	2003	mg/kg	-	4.0	-	4.5
CFPP (if used as blend component for diesel fuel)	DIN EN 116	2015	°C	from 15.04. to 30.09.	0	-	1.8
				from 01.10. to 15.11.	-5	-	-3.1
				from 16.11. to 28/29.02.	-10	-	-7.9
				from 01.03. to 14.04	-5	-	-3.1
Cloud point (if used as blend component for diesel fuel)	DIN EN 23015	1994	°C	from 15.04. to 30.09.	5	-	7.4
				from 01.10. to 15.11.	0	-	2.4
				from 16.11. to 28/29.02.	-3	-	-0.6
				from 01.03. to 14.04	0	-	2.4



**Table 2: Limits and test methods for the parameters tested according to the QM system of AGQM.**

Test Parameter	Method	Year of Publication	Unit	Standard Limits		Acceptance Limits	
				min.	max.	min.	max.
Water content (for producers)	DIN EN ISO 12937	2002	% (m/m)	-	0.027	-	0.034
Water content (for traders)	DIN EN ISO 12937	2002	% (m/m)	-	0.032	-	0.039
Total contamination	DIN EN 12662	1998 <sup>2</sup>	mg/kg	-	20	-	20
CFPP (if used as blend component for diesel fuel)	DIN EN 116	2015	°C	from 19.10. to 28/29.02	-10	-	-7.9

<sup>2</sup> Due to the fact that the current version of DIN EN 12662 is not suitable for the determination of the total contamination of FAME, DIN EN 12662:1998 applies until further notice.



**Table 3: Limits and test methods for the tested parameters for blend component for biodiesel according to the QM system of AGQM.**

Test Parameter	Method	Year of Publication	Unit	Standard Limits		Acceptance Limits	
				min.	max.	min.	max.
Sulfur Content	DIN EN ISO 20846	2011	mg/kg	-	20	-	20
Cloud point	DIN EN 23015	1998	°C	-	15	-	17.4
CFPP	DIN EN 116	2015	°C	-	10	-	11.4